

European Organisation for Technical Approvals
Europäische Organisation für Technische Zulassungen
Organisation Européenne pour l'Agrément Technique

Established pursuant to Annex II of the Council Directive 89/106 of 21 December 1988 on the approximation of laws, regulations and administrative provisions of Member States relating to construction products (Construction Products Directive)

ETAG 022

GUIDELINE FOR EUROPEAN TECHNICAL APPROVAL of

Watertight covering kits for wet room floors and or walls

Part 2: Kits based on flexible sheets

Version November 2010

This Guideline for European Technical Approval is established and published in accordance with Article 11 of the Construction Products Directive as a basis for the preparation and issue of European Technical Approvals in accordance with Article 9.1 of the Construction Products Directive.

European Technical Approvals are issued by approval bodies authorised and notified in accordance with Article 10 of the Construction Products Directive. These bodies are organized in EOTA.

The European Technical Approval, according to the Construction Products Directive, is a favourable technical assessment of the fitness for use of a construction product and the technical specification of the assessed product, serving as basis for the CE marking of this product when and where a harmonised standard according to the Directive is not or not yet available.

Due to technical innovation and the progress of the state of the art, guidelines for technical approval might not reflect the latest developments and experiences gained in approval procedures. The reader of this Guideline is therefore advised to check with an EOTA member whether there are further provisions which have to be taken into account in the use of the Guideline.

Copy right: EOTA

Note: The copy right refers to the English reference version established by EOTA. For publications in accordance with Article 11.3 of the Construction Products Directive the national laws, regulations and administrative provisions of the Member State concerned are applicable.

Table of contents

1 SCOPE OF THE ETAG

- 1.1 Definition of the construction product
- 1.2 Intended use of the construction product
 - 1.2.1 General
 - 1.2.2 Substrates
- 1.3 Assumed working life of the construction product
- 1.4 Terminology
 - 1.4.1 Common terms relating to the Construction Products Directive
 - 1.4.2 Specific terms used in this ETAG
- 1.5 Procedure in the case of a significant deviation from the ETAG

2 Assessment of fitness for use

- 2.1 Meaning of "fitness for use"
- 2.2 Elements of the assessment of fitness for use
- 2.3 Relationship of requirements to the characteristics of the assembled system and its components and methods of verification and assessment
- 2.4 Characteristics of the assembled system, which are relevant for the fitness for use
 - 2.4.1 Reaction to fire
 - 2.4.2 Release of dangerous substances
 - 2.4.3 Vapour permeability
 - 2.4.4 Moisture resistance
 - 2.4.4.1 Water tightness
 - 2.4.4.2 Crack bridging ability
 - 2.4.4.3 Bond strength
 - 2.4.4.4 Scratching resistance
 - 2.4.4.5 Joint bridging ability
 - 2.4.4.6 Water tightness around penetrations
 - 2.4.4.7 Joint strength
 - 2.4.4.8 Flexibility
 - 2.4.5 Slipperiness
 - 2.4.6 Durability
 - 2.4.6.1 Dimensional stability
 - 2.4.6.2 Resistance to temperature
 - 2.4.6.3 Resistance to water
 - 2.4.6.4 Resistance to alkalinity
 - 2.4.6.5 Resistance to chemical agents
 - 2.4.6.6 Resistance to biological agents
 - 2.4.6.7 Resistance to mechanical wear
 - 2.4.7 Serviceability
 - 2.4.7.1 Cleanability
 - 2.4.7.2 Repairability
 - 2.4.7.3 Thickness
 - 2.4.7.4 Applicability
- 2.5 Components and their characteristics, which are relevant for the fitness for use

3 EVALUATION AND ATTESTATION OF CONFORMITY AND CE MARKING

- 3.1 Systems of conformity attestation
- 3.2 Tasks and responsibilities of the manufacturer and notified bodies
- 3.3 CE marking and accompanying information

4 Assumptions under which the fitness for the intended use is assessed

- 4.1 Manufacturing of the kit
- 4.2 Packaging, transport, storage of the kit

- 4.3 Installation of the kit in the works
- 4.4 Use, maintenance, repair

5 Identification of the construction product

- 5.1 Means of identification
- 5.2 Product characteristics used for identification checking
 - 5.2.1 Flexible sheet
 - 5.2.2 Adhesives
 - 5.2.2.1 Thermographic analysis
 - 5.2.3 Primers
 - 5.2.3.1 Infrared spectrometry
 - 5.2.3.2 Viscosity
 - 5.2.3.3 Density
 - 5.2.3.4 pH-value
 - 5.2.4 Reinforcements
 - 5.2.4.1 Tensile strength and elongation

6 Format of ETAs issued on the basis of the ETAG

7 Reference documents

- Annex A Water tightness around penetrations and other details in wet room floors with flexible substrates**
- Annex B Impermeability when subjected to movement of the underlying material – tensile and shear loading**
- Annex C Test for scratching resistance**
- Annex D Not relevant for this part**
- Annex E Walls in wet rooms: Water tightness and resistance to water and moisture of walls with flexible substrate**
- Annex F Water tightness around penetrations and other details in wet room walls with flexible substrate**
- Annex G Water tightness around penetrations and other details in wet room walls and floors with rigid substrates**
- Annex H Not relevant for this part**

1 SCOPE OF THE ETAG

1.1. Definition of the construction product

A "kit" is a special form of a "construction product" in the sense of the CPD. It consists of several "components" which are

- Placed on the market with a common CE marking,
- Assembled on site, and
- Thus become an "assembled system" installed in the construction works.

Individual components of a kit may be separately available on the market. Such a component may itself, as a construction product in the sense of the CPD, bear the CE marking on its own right on the basis of a product hEN or ETA. Nevertheless, it may need to be assessed again as a component of the kit.

The Guideline covers watertight covering kits for interior wet room floors and/or walls. The watertight covering is placed on the inner surface of the wet room floor or wall. A screed or render may be installed over the flexible sheet which may itself form the wearing layer of the installed system or which may be covered by another product, e.g. ceramic tiles. This possible wearing layer is not part of the kit. See also Commission Guidance paper C on kits and systems.

Components covered by this guideline can already be CE marked in their own right according to EN 14041, EN 13967, EN 13956, EN 13969 or EN 13707 and consequently some of the component characteristics have already been determined. However an assessment of the components as part of the kit still needs to be carried out according to this guideline.

This part 2 of the Guideline covers kits, which can be supplied as single- or multi layer flexible sheets with possible associated adhesives, welding material etc.

The sheets may be partly or fully bonded or loose laid.

The sheets can be with or without a reinforcement and/or surface treatment to facilitate adherence to substrate and/or other additional components, e.g. ceramic tiles. Furthermore, the sheets can have a smooth surface or be made with different types of profiling.

The joints between the sheets are made by welding, adhering etc.

Other parts of the Guideline cover kits, which can be supplied as:

- Kits, which can be supplied as single- or multi component liquid waterproofing membranes with possible associated adhesives, primers etc. and jointless coverings such as paint systems, glass fibre reinforced polyester, polyurethane or epoxy (Part 1).
- Kits of inherently watertight boards including jointing bands (Part 3).

The kits include any associated components specified by the applicant such as glues, welding bands and sealants for the joints and possible reinforcements for penetrations, gullies etc. If a wearing surface of tiles is foreseen the tile adhesive(s) shall be specified and subject to relevant assessment.

Pipes and floor gullies themselves are not part of the kit.

Ceramic tiles and their jointing material, e.g. grouts, are not part of the kit.

Sealing of penetrations can be executed with the actual watertight covering product, separate sealants, sealing strips or collars acting together with the waterproofing product.

The kit shall at least resist stresses caused by movements of construction elements acting as substrate and resist the influence of water, temperature variations, and alkalinity of concrete and ceramic tile mortars.

The exact composition of watertight coverings may vary with the type of use and with the type of substrate with which the covering shall perform in a hygrothermally, mechanically and chemically satisfactory manner.

The components of the kit are manufactured in a factory and are assembled on site as a waterproofing system.

This Guideline does not cover watertight coverings for swimming pools and industrial processes.

This Guideline does not cover watertight coverings intended to be resistant to extreme chemical or biological exposures, such as can be expected in industrial kitchens and industrial processes, and claims to this effect by the applicant cannot be assessed in accordance with this ETAG.

1.2 Intended use of the construction product

1.2.1 General

The intended uses of the coverings kits are:

Indoor applications, where the kit is not exposed to temperatures (i.e. temperature of structure) below 5 °C and above 40 °C, in the following uses:

Floor and/or wall surfaces with only occasional direct exposure to water, e.g. at a good distance from shower or bathtub.

Floors and/or walls in shower areas or around bathtubs used for a few showers daily, e.g. in ordinary dwellings, multi-family houses and hotels

Floor and/or wall surfaces with exposure to water more frequent or of longer duration than normally anticipated in dwellings, e.g. public wet rooms, schools and sport facilities.

The various intended uses indicated above do not lead to different assessment criteria and the ETA will cover all intended uses. However, the use may be limited due to national legislation in the Member States.

1.2.2 Substrates

The actions on the assembled watertight covering system, which influence a durable watertight function, depend also on the function and type of substrate. The following table is not an exhaustive list of substrates but only indicates the tests related to the type of substrate.

In general the substrates fall in different types:

Table 1: Different types of substrates and the corresponding system tests

	Substrates (usually “rigid”), homogenous but susceptible to cracking	Substrates (usually “flexible”) not susceptible to cracking but with jointing¹	Substrates (usually “rigid”) susceptible to cracking and with jointing¹
Moisture sensitive substrates	<p>Examples: Gypsum blocks</p> <p>Tests: 2.4.4.2 Assessment Category 1, 2, 3 2.4.4.6, Assessment Category 1 or 2 with annex G</p>	<p>Examples: Gypsum boards, Wood based materials</p> <p>Tests: 2.4.4.5, Assessment Category 1 or 2 2.4.4.6, Assessment Category 1 or 2 with annex A and F, or E</p>	None known
Non moisture sensitive substrates	<p>Examples: In-situ concrete, masonry</p> <p>Tests: 2.4.4.2 Assessment Category 1, 2, 3 2.4.4.6, Assessment Category 1 or 2 with annex G</p>	<p>Examples: Calcium silicate boards, fibre cement boards</p> <p>Tests: 2.4.4.5, Assessment Category 1 or 2 2.4.4.6, Assessment Category 1 or 2 with annex A and F, or E</p>	<p>Examples: Concrete or aerated concrete elements</p> <p>Tests: 2.4.4.2 Assessment Category 1, 2, 3 2.4.4.5, Assessment Category 1 or 2 2.4.4.6, Assessment Category 1 or 2 with annex G</p>

The decision on whether to apply assessment category 1, 2 or 3 in 2.4.4.2 or assessment category 1 or 2 in 2.4.4.5 and 2.4.4.6 depends on the national requirements. These can apply to the strength and stability of the substrate and to the security for the waterproofing system dependent on the nature of the substrate (moisture sensitive/not moisture sensitive).

¹ For substrates with un-reinforced filled jointing, the crack bridging ability test has to be performed according to 2.4.4.2

1.3 Assumed working life of the construction product

The provisions and the verification and assessment methods included or referred to in this ETAG have been written based upon the assumed working life of the watertight covering kits for the intended use of 25 years, provided that the watertight coverings kit is subject to appropriate installation, use and maintenance (see 4). These provisions are based upon the current state of art and the available knowledge and experience.

"Assumed working life" means that it is expected that, when an assessment following the ETAG-provisions is made, and when this working life has elapsed, the real working life may be, in normal use conditions, considerably longer without major degradation affecting the Essential Requirements².

The indications given as to the working life of a watertight covering kit cannot be interpreted as a guarantee given by the producer or the approval body. They should be regarded only as a means for choosing the appropriate criteria for watertight covering kits in relation to the expected economically reasonable working life of the works (see 5.2.2 of Interpretative Documents).

1.4 Terminology

1.4.1 Common terms relating to the Construction Products Directive

For the meaning of these terms see EOTA document "Common terms used in Guidelines for European Technical Approval" published on the EOTA website.

1.4.2 Specific terms used in this ETAG

1.4.2.1 Wet room

Wet rooms are rooms where the floor and possibly the walls are frequently exposed to water, e.g. bathrooms, sculleries or washing rooms.

1.4.2.2 Manufacturer's technical dossier (MTD)

A document, or collection of documents, consisting of the Factory Production Control (setting out the specific quality practices, resources and sequence of activities), the design rules, the application methods (including procedures for quality control on site), build-up/composition of the kit, characteristics of a possible wearing surface and the directions concerning maintenance and repair of the assembled system, relevant to a particular product or a range of products. Confidential information may be given in a confidential part of the MTD.

1.4.2.3 Batch

A limited amount of materials made in a single production process e.g. one mix of a waterproofing component.

1.4.2.4 Production sequence

Continuous period of time in which a single component is manufactured, e.g. the time in which 8 batches are produced.

1.4.2.5 Wearing surface

A protective layer applied in liquid or solid form used over a watertight covering in order to protect it from mechanical wear and allowing pedestrian access

² The real working **life** of a product incorporated in a specific works depends on the environmental conditions to which that works is subject and the particular conditions of the design, execution, use and maintenance of that works **may be outside this ETAG**. Therefore, it cannot be excluded that **in these** cases the real working life of the product may also be shorter than the assumed working life.

- 1.4.2.6 Watertight
- A property related to the characteristics of the assembled system meaning that no liquid water shall penetrate after exposure to water.
- 1.4.2.7 Tile
- A rigid surface layer meant for protection of the substrate and/or for decorative purposes e.g. ceramic tiles in accordance with EN 14411.
- 1.4.2.8 Flexible sheet
- A sheet in e.g. roll form forming a resilient watertight covering, e.g. bituminous, elastomeric or plastic sheet. The sheet can also constitute the wearing surface.
- 1.4.2.9 Watertight boards
- Boards which in themselves or due to a factory applied surface treatment are inherently watertight.
- 1.4.2.10 Crack
- A crack in the sense of this guideline is an unpredictable opening/gap in the substrate, e.g. cracks caused by shrinking of concrete. Cracks may occur in the material used to fill joints between elements, e.g. in mortar
- 1.4.2.11 Jointing
- Jointing is a deliberate act of connecting two or more elements forming the substrate. Jointing can be unfilled, e.g. between two gypsum boards or can be filled e.g. with mortar between two concrete elements. Jointing in the substrate can be reinforced.
- 1.4.2.12 Joint
- A joint is a discontinuity in the substrate. In the sense of this ETAG the phrase “joint” does not include movement joints, such as shrinkage joints, expansion joints and structural joints or mortar joints in masonry
- 1.4.2.13 Moisture sensitive
- In the sense of this ETAG it means that the substrate will deteriorate under the continuous influence of moisture
- 1.4.2.14 Adhesive
- In the context of this part of the ETAG an adhesive is understood to be a bonding agent for adhering the flexible sheet to the possibly pre-treated substrate and/or the wearing surface to the flexible sheet. In some cases the adhesive can also act as a primer.
- 1.4.2.15 Primer
- In the context of this part of the ETAG a primer is understood to be a pre-treatment of the substrate which in some cases also can act as an adhesive.

1.5 Procedure in the case of a significant deviation from the ETAG

The provisions of this ETAG apply to the preparation and issue of European Technical Approvals in accordance with Art. 9.1 of the CPD and section 3.1 of the Common Procedural Rules.

In cases in which a certain provision of this ETAG is not wholly or partially applicable, or a particular aspect of a product and/or intended use to be assessed is not wholly or sufficiently covered by the methods and criteria of the ETAG, the procedure of Art. 9.2 of the CPD and section 3.2 of the Common Procedural Rules apply with regard to the deviation or aspect concerned.

2 ASSESSMENT OF FITNESS FOR USE

2.1 Meaning of "fitness for use"

"Fitness for use" or "fitness for the intended use" of a construction product means that the product has such characteristics that the works in which it is to be incorporated, assembled, applied or installed, can, if properly designed and built,

- Satisfy the Essential Requirements when and where such works are subject to regulations containing such requirements (CPD Art. 2.1) and
- Be fit for their intended use, account being taken of economy, and in this connection satisfy the Essential Requirements for an economically reasonable working life, if normally maintained (CPD Annex I, Preamble).

In the case of kits, "fitness for (the intended) use" refers to

- a) the assembled system (it must have "such characteristics that the works in which it is to be incorporated, assembled, applied or installed, can, if properly designed and built, satisfy the Essential Requirements when and where such works are subject to regulations containing such requirements")
- b) The components of the assembled system (each of the components, including those which are not included in the kit, if any, must have such characteristics that the assembled system can, if properly assembled, be fit for the intended use in the sense of clause a above).

2.2 Elements of the assessment of fitness for use

The assessment of the fitness of a construction product for its intended use includes:

- The identification of the characteristics of the assembled system which are relevant to its fitness for use (and for which the NPD option is not applicable);
- The establishment of methods for the verification and assessment of the characteristics of the assembled system and the expression of the respective performances;
- The identification of characteristics to which the option "No Performance Determined" applies for the reason that in one or more Member States they are not relevant for the fulfilment of the requirements applicable to the works;
- The identification of characteristics for which limit values (threshold values) have to be respected for technical reasons.

With regard to the applicable legislation in the Member States the assessment of the kit has to be done for the product- and/ or the system-characteristics to fulfil requirements for the performance of the product depending on the intended use of the product and the kind of substrate and aspects of security (consequences of water permeability for the works e.g. depending on moisture sensitive or not moisture sensitive substrates) (see para 1.2.2)

Not every characteristic has to be proven if it is not required in at least one of the member states (npd option). For fundamental characteristics for which limiting values have to be respected for technical reasons the npd option is not possible.

2.3 Relationship of requirements to the characteristics of the assembled system and its components and methods of verification and assessment

The system and component characteristics, methods of verification and assessment criteria, which are relevant for the fitness of watertight coverings kits for the intended use(s) referred to in 1.2 are given in Table 2.

Table 2: Characteristics of the assembled system and methods of verification and assessment

Number	Product characteristic	Option "No Performance Determined"	Method of verification and assessment	Expression of test result (value, class, NPD, criterion, etc)
(1)	(2)	(3)	(4)	(5)
Essential Requirement 1 Mechanical resistance and stability				
	Not relevant			
Essential Requirement 2 Safety in case of fire				
1	Reaction to fire	Yes	2.4.1	Euroclass A1 – F or A1 _n – F _n
Essential Requirement 3 Hygiene, health and environment				
2	Release of dangerous substances	Yes	2.4.2	Statement by applicant
3	Vapour permeability	Yes	2.4.3	Declared value
4	Moisture resistance		2.4.4	
4.1	Water tightness	No	2.4.4.1	Pass/fail (No penetration of water)
4.2	Crack bridging ability**)	Substrates susceptible to cracks: No Substrates not susceptible to cracks: Yes	2.4.4.2	Pass/fail Assessment category 0 (no test) Assessment category 1 (0,4 mm) Assessment category 2 (0,75 mm) Assessment category 3 (1,5 mm)
4.3	Bond strength	No	2.4.4.3	Pass/fail Assessment category 0 (no test) Assessment category 1 (> 0,2 MPa) Assessment category 2 (> 0,3 MPa) Assessment category 3 (≥ 0,5 MPa)
4.4	Scratching resistance	Yes	2.4.4.4	Pass/fail (No visual penetration)
4.5	Joint bridging ability**)	Substrates with joints: No Substrates without joints: Yes	2.4.4.5	Pass/fail Assessment category 0, 1 or 2
4.6	Water tightness around penetrations*)**)	No	2.4.4.6	Pass/fail Assessment category 1 or assessment category 2
4.7	Joint strength	Yes	2.4.4.7	Declared value
4.8	Flexibility	Yes	2.4.4.8	Pass/fail
Essential Requirement 4 Safety in use				
5	Slipperiness	Yes	2.4.5	Declared value
Essential Requirement 5 Protection against noise				
	Not relevant			
Essential Requirement 6 Energy economy and heat retention				
	Not relevant			
General aspects relating to fitness for use ¹				
6	Durability		2.4.6	

6.1	Dimensional stability	No	2.4.6.1	Declared value
6.2	Resistance to temperature	No	2.4.6.2	Pass/fail
6.3	Resistance to water	No	2.4.6.3	Pass/fail Assessment category 0 (no test) Assessment category 1 (> 0,2 MPa) Assessment category 2 (> 0,3 MPa) Assessment category 3 (\geq 0,5 MPa)
6.4	Resistance to alkalinity	No	2.4.6.4	Assessment category 1 (80EC, 4 weeks) Assessment category 1 (50EC, 16 weeks) Assessment category 1 (23EC, 16 weeks)
6.5	Resistance to chemical agents	Yes	2.4.6.5	Assessment
6.6	Resistance to biological agents	Yes	2.4.6.6	Assessment
6.7	Resistance to mechanical wear	Yes	2.4.6.7	Declared value
7	Serviceability		2.4.7	
7.1	Cleanability	Yes	2.4.7.1	Declared value
7.2	Reparability	Yes	2.4.7.2	Statement
7.3	Thickness	No	2.4.7.3	Declared value
7.4	Applicability	No	2.4.7.4	Declaration
1) Aspects of durability and economy of the works (see CPD Annex 1, sentence 1 and 2)				
*) This characteristic also relates to the durability of the kit				
**) The relevance of this test depends on the substrate covered by the intended use, see paragraph 1.2.2				

Adaptation of the general test regime to a specified waterproofing system on the basis of national requirements

Under consideration of national requirements for the evaluation of the watertight covering kit (required characteristics and assessment categories depending on the kind of substrate, see 1.2.2) and on the basis of the general test regime above the test regime for the provided use and application conditions for a waterproofing system which shall be approved has to be specified. The characteristics linked with the npd option "NO" have to be proven in any case. The characteristics linked with the npd option "Yes" have to be proven only if there is a requirement in the member state to which the product shall be marketed.

It should be noted that some member states have prescriptive requirements for certain characteristics given in the ETA, e.g. for moisture in buildings and building elements or water vapour resistance. This should be investigated by the applicant and the approval body in relation to the intended market.

2.4 Characteristics of the assembled system, which are relevant for the fitness for use

If the flexible sheet has been CE marked in accordance with harmonised standards, some of the below mentioned tests may not be necessary, provided that the relevant characteristic has been determined in connection with the CE marking.

2.4.1 Reaction to fire

2.4.1.1 Method of verification

Where required, the kit shall be tested and classified in its end use conditions in accordance with EN 13501-1:2007.

When tested according to EN ISO 11925-2, the kits shall be tested under conditions of surface flame attack.

NOTE In those cases in which the SBI test may be inappropriate, it is currently considered that the Euroclasses Classification system at Classes D and above requires investigation to determine its appropriateness. Pending results of such an investigation and discussions in the Fire Expert Group, these cases are tested according to EN ISO 11925-2.

2.4.1.2 Method of assessing and judging

The kit shall be classified according to EN 13501-1:2007 in its end use conditions (assembled system in which the kit is intended to be incorporated).

It shall be noted in the ETA which components of the kit have been tested and classified.

Where national regulation exists for any of the components of the kit or the kit itself as a part of the assembled system (e.g. assembled system with a wearing layer not part of the kit), this component or the kit itself shall be classified according to EN 13501-1:2007.

2.4.2 Release of dangerous substances

2.4.2.1 Method of verification

Presence of dangerous substances in the product

The applicant shall submit a written declaration stating whether or not the product/kit contains dangerous substances according to European and national regulations, when and where relevant in the Member States of destination, and shall list these substances.

Compliance with the applicable regulations

If the product/kit contains dangerous substances as declared above, the ETA will provide the method(s) which has been used for demonstrating compliance with the applicable regulations in the Member States of destination, according to the dated EU data-base (method(s) of content or release, as appropriate).

2.4.2.2 Method of assessing and judging

The product/kit shall comply with all relevant European and national provisions applicable for the uses for which it is brought to the market. The attention of the applicant should be drawn on the fact that for other uses or other Member States of destination there may be other requirements, which would have to be respected. For dangerous substances contained in the product but not covered by the ETA, the NPD option (no performance determined) is applicable.

2.4.3 (Water) Vapour permeability

2.4.3.1 Method of verification

The test is carried out in accordance with EN/ISO 12572. The test shall be performed as described in annex C of the standard. The tests shall be carried out with climatic conditions as described for option C in chapter 7 of the standard.

If a primer or adhesive etc. is claimed to have an influence on the water vapour permeability, the test shall be carried out on a sample made of gypsum plasterboard with approximately 12,5 mm thickness and a density of approximately 720 kg/m³ including both watertight covering and primer/adhesive.

The application of the watertight covering kit shall be in accordance with the manufacturer's instructions. A possible wearing surface shall not be included in the sample.

Where the membrane is already CE marked and tested in accordance with EN 1931, it is not necessary to repeat the tests. However, assessment still has to be carried out according to this Guideline to ensure that the membrane is fit for the intended use.

2.4.3.2 Method of assessing and judging

Declared value with reference to the used test method and the applied climatic conditions.

2.4.4 Moisture resistance

2.4.4.1 Water tightness

2.4.4.1.1 Method of verification

For bituminous or polymeric sheets the test is carried out in accordance with EN 1928 method A or B. Testing shall be performed with a pressure as indicated in the relevant corresponding harmonised standard.

For resilient floor and wall coverings of polyvinyl chloride the water tightness of the watertight covering kit is determined in accordance with EN 13553.

Where the membrane is already CE marked and tested in accordance with the corresponding test methods, it is not necessary to repeat the tests.

2.4.4.1.2 Method of assessing and judging

Pass/fail.

2.4.4.2 Crack bridging ability

2.4.4.2.1 Method of verification

The test is carried out when the intended use covers substrates susceptible to cracking, see paragraph 1.2.2. and footnote **) of table 2.

- For fully or partially bonded sheets the test is necessary where special precautions for bridging joints in the substrate are prescribed for the kit, e.g. reinforcement, or for substrates where joint bridging test is not required. In all other cases the crack bridging ability will be covered by the assessment of the joint bridging ability and the consequent assessment category for crack bridging will be 3.
- For loose laid or mechanically attached sheets this test is not required.

For substrates not susceptible to cracks but where a filled joint can be foreseen, and this joint could lead to cracks in the substrate, the test shall also apply.

The test is carried out in accordance with the method described below:

Testing shall be carried out following the method C.2 of prEN 1062-7 with the following precisions. The substrates are reinforced concrete slabs, which are manufactured as described in chapter C.2.2 of the above mentioned standard. The watertight covering shall be applied onto three of these substrates.

Application of the waterproofing sheet

The application of the watertight covering shall take place in a strip of 150 mm over the entire length of the slab so that at the longitudinal edges 25 mm wide strips remain uncovered for observing the cracks in the substrate (surface length \times width = 300 mm \times 200 mm).


Storage of the prepared test specimen

28 days dry at standard atmosphere 23 ± 2 °C / 50 ± 5 % RH.

Testing

After storage the test specimen shall be loaded in a bending test apparatus with way/distance control with the load arrangement as shown in figure 1.

Figure 1. Test set-up for generating cracks by bending of test specimen. Dimensions in mm

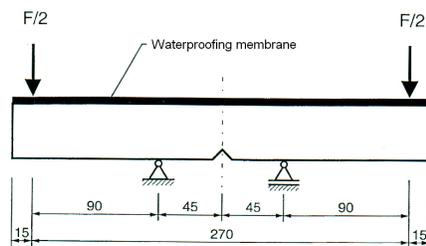

Bending of the test specimen shall be increased constantly by applying a force F until a crack appears on the uncovered sides of the concrete surface. The crack shall appear on both sides of the concrete, close to the edge of the watertight material. The velocity of the crack opening shall be arranged that 20 minutes from the point of time a crack is recognizable in the concrete (possible appearance of a light zone in the watertight material) a crack width of 0,4 mm, 0,75 mm or 1,5 mm respectively (depending on the assessment category) is reached (0,02 mm/min.). The crack shall be measured – for example using a graduated magnifying glass. The crack size has to be fixed. Each type of change during the following 24 h (incipient crack, tear or through crack) shall be stated in the test report.

Assessment category 0: The test is irrelevant (loose laid sheets etc.)

Assessment category 1: Crack width in test: 0,4 mm

Assessment category 2: Crack width in test: 0,75 mm

Assessment category 3: Crack width in test: 1,5 mm or joint bridging test passed

2.4.4.2.2 Method of assessing and judging

For all assessment categories the test is passed if, 24 h after fixing the crack in the substrate no perforation or through crack (damage) has occurred in the watertight covering.

2.4.4.3 Bond strength

2.4.4.3.1 Method of verification

The test is only applicable for fully or partially bonded sheets.

For kits intended to be covered by a ceramic tile wearing surface, the test is carried out in accordance with Paragraph A.6.2 in prEN 14891.

For kits not intended to be covered by a ceramic tile wearing surface the test is carried out with a square metal plate (50 × 50 mm) glued with a suitable high strength adhesive, e.g. solvent free epoxy directly to the watertight covering kit. The test is performed according to prEN 14891 concerning the speed.

Other substrates may be used upon agreement if the manufacturer recommends the substrate for the watertight covering kit. To demonstrate compatibility with other optional substrates, the membrane shall be applied to the selected substrate in accordance with the initial adhesion test method (A 6.2) in prEN 14891. When a result of more than or equal to the threshold values according to 2.4.4.3.2 is achieved or cohesive failure occurs in the substrate, the requirement is considered satisfied.

If several tile adhesives are envisaged, then a bond strength test is carried out for each tile adhesive on a concrete substrate with the watertight covering. If more than one substrate is covered by the intended use, then bond strength tests are carried out on every substrate, but only with one adhesive.

2.4.4.3.2 Method of assessing and judging

Assessment category 0: The test is irrelevant (loose laid sheets etc.)

Assessment category 1: The bond strength on concrete shall be higher than or equal to 0,2 MPa .

Assessment category 2: The bond strength on concrete shall be higher than or equal to 0,3 MPa

Assessment category 3: The bond strength on concrete shall be higher than or equal to 0,5 MPa

2.4.4.4 Scratching resistance

2.4.4.4.1 Method of verification

The scratching resistance of the watertight covering kit is determined in accordance with annex C.

The test is only carried out on kits without an envisaged wearing surface. The test applies for both floor and wall applications.

2.4.4.4.2 Method of assessing and judging

Pass/fail

2.4.4.5 Joint bridging ability

2.4.4.5.1 Method of verification

The test is only carried out when the intended use covers substrates susceptible to joint movements, see paragraph 1.2.2, i.e. joints in substrates that are not filled, such as between boards.

Loose laid or mechanically fixed sheets need not to be tested.

The joint bridging ability of flexible sheets for both floors and/or walls with and without wearing surface at joints subjected to movement of the substrate shall be evaluated based on:

Assessment category 0: The test is irrelevant (loose laid sheets etc.)

Assessment category 1: Judging by the approval body based on the descriptions and drawings in the manufacturer's technical dossier (MTD) that sealings with the components of the kit may be established properly to fulfil the requirements on the assembled waterproofing system.

Assessment category 2: additional to assessment category 1 testing is performed in accordance with the principles in annex B with a 2 mm gap.

2.4.4.5.2 Method of assessing and judging

Indication of assessment category

2.4.4.6 Water tightness around penetrations

2.4.4.6.1 Method of verification

The water tightness of the flexible sheets for both floors and/or walls with and without wearing surface around penetrations, such as floor gullies; pipes and corners etc. may be determined in one of two categories of assessment.

Assessment category 1: Judging by the approval body of the descriptions and drawings in the manufacturer's technical dossier (MTD) that sealings with the components of the kit may be established properly to fulfil the requirements on the assembled waterproofing system.

Assessment category 2: Additional to assessment category 1 a test is performed for flexible substrates with joints in accordance with both annex A and annex F or for rigid substrates without joints in accordance with Annex G, see paragraph 1.2.2.

Products tested according to annexes A and F for flexible substrates do not need to be further tested according to annex G to comply with the assessment criteria for rigid substrates without joints.

For kits only for use on floors, the assessment shall be carried out on the basis of test according to annex A or G depending on the substrate.

For kits only for use on walls, the assessment shall be carried out on the basis of test according to annex G or E depending on the substrate.

When testing in accordance with annex A, G or E, the specimen shall include joints in the floor and the wall. The test shall reflect the most severe joint geometry envisaged by the manufacturer's installation instructions, e.g. including joints in the connections wall/wall and floor/wall and in a corner between a floor and 2 walls (if relevant).

If reparability of the covering is claimed by the manufacturer (see 2.4.7.2) it shall be considered during this test.

2.4.4.6.2 Method of assessing and judging

Indication of assessment category

2.4.4.7 Joint strength

2.4.4.7.1 Method of verification

For resilient floor and wall coverings of polyvinyl chloride the joint strength of the watertight covering kit is determined in accordance with EN 684.

For bituminous and polymeric sheets for both floors and/or walls the test is carried out in accordance with EN 12317-1 for bituminous sheets and EN 12317-2 for polymeric sheets (shear resistance).

Where the membrane is already CE marked and tested in accordance with the above mentioned test method, it is not necessary to repeat the tests.

2.4.4.7.2 Method of assessing and judging

Declared value.

2.4.4.8 Flexibility

The test is only relevant if the applicant describes solutions requiring bending of the sheet, e.g in the detail floor/wall.

2.4.4.8.1 Method of testing

The assessment is carried out for kits both with and without a wearing surface.

For flexible sheets for both floors and/or walls the test is carried out in accordance with EN 435.

Where the membrane is already CE marked and tested in accordance with the above mentioned test method, it is not necessary to repeat the tests.

2.4.4.8.2 Method of assessing and judging

When bent around a mandrel of 10 mm diameter, no cracking or other surface deterioration shall be visible with the naked eye.

2.4.5 Slipperiness

2.4.5.1 Method of verification

This test is only relevant for the wearing surface. Verification of slip resistance of flooring materials shall be undertaken in accordance with the relevant EN-standards prepared or under preparation by CEN/TC 339.

2.4.5.2 Method of assessing and judging

When this performance is determined the slip resistance of finished floorings shall be declared according to the relevant standard for the specified flooring product.

2.4.6 Durability

The following tests and assessments apply for kits with or without wearing surface as specified in the below text.

If the wearing surface is in the form of tiles and adhesive and if several tile adhesives are envisaged, then the assessments mentioned below are carried out for each adhesive on a concrete substrate with the watertight covering. This assessment will be valid for all substrates. However, if concrete is not considered to be an appropriate substrate, then an alternative can be agreed between the approval body and the applicant.

2.4.6.1 Dimensional stability

2.4.6.1.1 Method of verification

The assessment is carried out for kits both with and without a wearing surface.

For floor and wall coverings of polyvinyl chloride the dimensional stability of the watertight covering kit is determined in accordance with EN 434.

For kits with bituminous and polymeric sheets for floors and/or walls the dimensional stability of the watertight covering kit is determined in accordance with EN 1107-1 for bituminous sheets and EN 1107-2 for polymeric sheets.

Where the membrane is already CE marked and tested in accordance with the above mentioned test method, it is not necessary to repeat the tests.

2.4.6.1.2 Method of assessing and judging

Declared value.

2.4.6.2 Resistance to temperature

2.4.6.2.1 Method of verification

The resistance to temperature of the watertight covering kits with or without a wearing surface is determined in accordance with the following procedure:

Exposure is heat ageing performed in accordance with EN 1296. The exposure period is 4 weeks (at 70° C).

The tensile strength and elongation is determined on exposed and unexposed materials respectively according to EN 12311-1 for bituminous materials, EN 12311-2 for unreinforced and EN 13859-1 for reinforced polymeric materials.

The test is carried out for all intended uses.

Where the membrane is already CE marked and tested in accordance with the above mentioned test method, it is not necessary to repeat the tests.

2.4.6.2.2 Method of assessing and judging

After exposure the tensile strength and elongation shall not deviate more than $\pm 20\%$ (relatively) from that of the unexposed specimens. If the deviation is more than 20 % further investigations may be required by the approval body in order to assess the durability.

2.4.6.3 Resistance to water

2.4.6.3.1 Method of verification

The resistance to water of watertight covering kits with a wearing surface and a (tile) adhesive, is determined in accordance with Paragraph A.6.3 in prEN 14891 for all adhesives specified by the applicant.

In all other cases the resistance to water is covered by the test according to Annex A, F, G or E.

2.4.6.3.2 Method of assessing and judging

After the test the bond strength criteria to the relevant assessment category mentioned in 2.4.4.3.2 shall be fulfilled.

If the resistance to water is assessed on the basis of the test according to annex A, F, G or E, the relevant criteria for these tests apply.

2.4.6.4 Resistance to alkalinity

2.4.6.4.1 Method of verification

The resistance to alkalinity of the watertight covering kit is determined in one of three categories of assessment accordance with the following procedure:

Assessment category 1: Ageing of the sample according to EN 1847 at 80 °C for 4 weeks.

Assessment category 2: Ageing of the sample according to EN 1847 at 50 °C for 16 weeks.

Assessment category 3: Ageing of the sample according to EN 1847 at 23 °C for 16 weeks.

The tensile strength and elongation is determined according to EN 12311-2 for unreinforced and EN 13859-1 for reinforced polymeric materials.

The test is required only for products used with an alkaline screed or tile adhesive applied over the sheet. The test is not relevant for bituminous materials.

2.4.6.4.2 Method of assessing and judging

The used assessment category shall be indicated.

After exposure the tensile strength and elongation shall not deviate more than $\pm 20\%$ (relatively) from that of the unexposed specimens. If the deviation is more than 20% further investigations may be required by the approval body in order to assess the durability.

2.4.6.5 Resistance to chemical agents

2.4.6.5.1 Method of verification

Within the scope of this ETAG, the applicable chemical agent is considered to be ordinary cleaning agents, which are generally basic. Therefore, the assessment of this characteristic is considered to have been taken into account in the assessments described in 2.4.6.4 for resistance to alkalinity.

Exposures to acid agents and particular claims for resistance to chemical agents are not covered by this ETAG.

2.4.6.5.2 Method of assessing and judging

Not applicable

2.4.6.6 Resistance to biological agents

2.4.6.6.1 Method of verification

Particular claims for resistance to particular biological agents or an enhanced resistance to biological agents are not covered by this ETAG.

The biological exposure in wet rooms will typically be in the form of mould growth on the wearing surface (tiles and grouts, which are not part of the kit) or on the substrate, if these are organic. Mould growth on the substrate is considered to be caused by inappropriate design of the wall or floor structure. Kits with a wearing surface are therefore not intended to have a particular biological resistance. For kits where the watertight covering is also the wearing surface, the biological resistance can be assessed based on the relevant standards for the membrane.

In the absence of standards, the assessment shall be based on the relevant European and national provisions applicable for the uses for which it is brought to the market. The attention of the applicant should be drawn on the fact that for other uses or other Member States of destination there may be other requirements, which would have to be respected

2.4.6.6.2 Method of assessing and judging

Assessment by approval body depending on the test

2.4.6.7 Resistance to mechanical wear

2.4.6.7.1 Method of verification

Only relevant for watertight covering kits without a wearing surface. The purpose of the test is to assess the resistance to wear

Verification of the resistance to mechanical wear of the wearing surface of the watertight covering kit shall be undertaken in accordance with the relevant EN-standards for the specified products, e.g. EN 660.

The test is carried out for all intended uses.

2.4.6.7.2 Method of assessing and judging

When this performance is determined, the mechanical wear resistance of the products shall be declared according to the relevant standard for the specified flooring product.

2.4.7 Serviceability

2.4.7.1 Cleanability

2.4.7.1.1 Method of verification

Only relevant for watertight covering kits without a wearing surface, i.e. those kits where the watertight covering is also the wearing surface

The test shall be carried out in accordance with the following procedure:

The test is carried out on two samples. The samples are prepared on two wood fibre boards with dimensions 430 mm long, 165 mm wide and 5 mm thick. The brightest colour of the covering shall be chosen, and where available, white shall be used.

The samples are conditioned for 30 days at standard atmosphere $23 \pm 2 \text{ }^\circ\text{C} / 50 \pm 5 \text{ \% RH}$.

To simulate the soil a solution made from 9 g of (mild hand) soap, 1 g of carbon black and 600 g of tap water is mixed.

1 ml of the soil solution is applied to the samples with a pipette to form a spot of approx 35 mm in diameter. The soil spot shall air dry at ambient temperature for three days.

One of the samples is not cleaned and left for reference. The other is cleaned according to the following procedure.

The sample is cleaned with a brush made with 20 000 – 25 000 evenly cut pigs hairs with a free length of 18 – 20 mm and a diameter of 0,10 – 0,15 mm. The brush size shall be 80 mm × 30 mm and the mass shall be 450 g ± 10 g.

The brush is fixed in an apparatus so that it is moved over the sample 330 mm back and forth at a speed equal to 33 – 45 cycles per minute. One cycle is 660 mm. The number of cycles shall be recorded.

The cleaning is performed in three steps:

Step 1: The sample is washed down for 1 minute with lukewarm tap water $30 - 35 \text{ }^\circ\text{C}$ with a water amount of 6 - 7 l/m at a distance from the tap of approx. 50 mm and at an angle of 45° . The soil spot shall not be touched and left to dry for 15 minutes. Any change compared to the reference sample is recorded.

Step 2: The sample is fixed in the cleaning apparatus with the covering system facing up and in a manner so that the brush can travel in the longitudinal direction of the sample. The brush is dipped in water and placed in the apparatus and set in motion over the sample.

After 20 cycles the cleaning is stopped and the sample is cleaned according to step 1. After 15 minutes drying the remaining soil spot is assessed against the grey scale.

Step 3. The sample is cleaned according to step 2, but the water is replaced with a cleaning agent made from 10 % cat ion active tenside with 4 % metasilicate/water 1:10 or the cleaning agent specified by the ETA applicant. The procedure in this step is repeated twice.

After 15 minutes drying the remaining soil spot is assessed against the grey scale.

2.4.7.1.2 Method of assessing and judging

The grey scale category is declared for each step of cleaning according to the below grey scale:

Classification	Classification according to NCS colour code system	Cleaning degree
100/70 %	6 500	0
100/60 %	5 750	1
100/50 %	5 000	2
100/40 %	4 500	3
100/30 %	3 000	4
100/20 %	2 500	5
100/10 %	1 500	6
100/0 %		7

2.4.7.2 Repairability

2.4.7.2.1 Method of verification

If the manufacturer claims certain provisions concerning repair of the sheet, the repair shall be made and this shall be assessed based on the tests already performed according to 2.4.4.6.

2.4.7.2.2 Method of assessing and judging

Statement by the approval body as to whether or not repair is possible.

2.4.7.3 Thickness

2.4.7.3.1 Method of verification

The thickness of the resilient coverings of e.g. polyvinyl chloride for walls and for bituminous and polymeric sheets for both floors and/or walls with and without wearing surface is determined in accordance with relevant standards e.g. EN 428, EN 429, EN 1849-1 and EN 1849-2 respectively.

Where the thickness of the membrane is already tested in accordance with the appropriate test it is not necessary to repeat the tests. However, assessment still has to be carried out according to this Guideline to ensure that the test method is appropriate and that the membrane is fit for the intended use.

2.4.7.3.2 Method of assessing and judging

Declared value

2.4.7.4 Applicability

2.4.7.4.1 Method of verification

The applicability of the watertight covering kit is determined by a visual inspection during sample preparation and control of the installation guide.

2.4.7.4.2 Method of assessing and judging

The approval body makes a declaration of the applicability of the kit.

2.5 Components and their characteristics, which are relevant for the fitness for use

No additional tests on components with regard to the assessment of the fitness for use are relevant. However, certain component characteristics are used for identification purposes, see chapter 5.

3 Evaluation and attestation of conformity and CE marking

3.1 Systems of conformity attestation

According to the decision 2003/655/EC, dated 2003-09-17 of the European Commission³ the following systems of conformity attestation apply to the watertight covering kits:

Product	Intended use	Levels or classes	Attestation of conformity system
Watertight covering kits for wetroom floors and walls	For building works	-	2+

Table 3: System of attestation of conformity applicable to Watertight covering kits for wetroom floors and walls

Attestation of conformity concerning the product properties, which have an influence on the waterproofing function

System 2+:

Declaration of conformity of the product by the manufacturer on the basis of:
(See Annex III.2.(ii), first possibility, of the CPD):

- (a) Tasks for the manufacturer:
 - (1) Initial type-testing of the product;
 - (2) Factory production control;
 - (3) Testing of samples taken at the factory in accordance with a prescribed test plan.
- (b) Tasks for the notified body:
 - (4) Certification of factory production control on the basis of:
 - Initial inspection of factory and of factory production control;
 - Continuous surveillance, assessment and approval of factory production control.

If reaction to fire is relevant in addition, according to the decision 2003/655/EC, dated 2003-09-17 of the European Commission the following systems of conformity attestation applies to watertight covering kits with regard to reaction to fire (the attestation of conformity system to be applied depends on the composition of the product):

Product(s)	Intended use(s)	Level(s) or class(es) (<i>reaction to fire</i>)	Attestation of conformity system(s)
<i>Watertight covering kits for wet room floors and walls</i>	For uses subject to regulations on reaction to fire	A1*, A2*, B*, C*	1
		A1**, A2**, B**, C**, D, E,	3
		(A1 to E) ***, F	4
System 1: See Directive 89/106/EEC Annex III.2.(i), without audit-testing of samples System 3: See Directive 89/106/EEC Annex III.2.(ii), Second possibility System 4: See Directive 89/106/EEC Annex III.2.(ii), Third possibility * Products/materials for which a clearly identifiable stage in the production process results in an improvement of the reaction to fire classification (e.g. an addition of fire retardants or a limiting of organic material) ** Products/materials not covered by footnote (*) *** Products/materials that do not require to be tested for reaction to fire (e.g. Products/materials of class A1 according to Commission Decision 96/603/EC, as amended)			

Table 4: Choice of the attestation of conformity system with respect to reaction to fire

³ Official Journal of the European Communities L 231/12

Attestation of Conformity of the product properties which have an influence on the reaction to fire for products with in table 2 specified classes and footnotes:

System 1

Certification of the conformity of the product by a notified certification body on the basis of:
(See Annex III.2.(i), of the CPD without audit-testing of samples)

- (a) Tasks for the manufacturer:
 - (1) Factory production control;
 - (2) Further testing of samples taken at the factory by the manufacturer in accordance with a prescribed test plan;
- (b) Tasks for the notified body:
 - (3) Initial type-testing of the product;
 - (4) Initial inspection of factory and of factory production control;
 - (5) Continuous surveillance, assessment and approval of factory production control.

System 3

Declaration of conformity of the product by the manufacturer on the basis of:
(See Annex III.2.(ii), Second possibility of the CPD)

- (a) Tasks for the manufacturer:
 - (1) Factory production control;
- (b) Tasks for the notified body:
 - (2) Initial type testing of the product.

System 4

Declaration of conformity of the product by the manufacturer on the basis of:
(Annex III.2. (ii), Third possibility of the CPD)

- (a) Tasks for the manufacturer:
 - (1) Initial type testing of the product;
 - (2) Factory production control.

3.2 Tasks and responsibilities of the manufacturer and notified bodies

In transposing the relevant systems of attestation of conformity to the approved kit the approval body has to lay down the specific tasks of the manufacturer and the notified body in the process of attestation of conformity in control plans.

Both large and small companies produce these products and there is a wide variation in the materials and test methods used. Therefore a precise test plan can only be set up on a case-by-case basis.

In general it is not necessary to conduct tests on complete kits or applied systems. Indirect methods will normally be sufficient, e.g. control of raw materials, manufacturing processes and properties of components.

The following gives general cornerstones on how to write these control plans for the product family of this ETAG. They shall be specified and filled in by the approval body for the approved product under consideration of the specified production process of the manufacturer.

It is assumed that the characteristics given in the following control plans have a correlation to the properties of the products both for the water tightening function and the reaction to fire.

3.2.1 Tasks of the manufacturer (Control plan)

Table 5: Examples of tasks of the manufacturer

Type of control		Test or control method	Minimum extent/frequency of control
AoC element (acc. to CPD Annex III.1)	Product, raw/constituent material, product component and characteristic concerned		
Factory production control (For all systems including testing of samples in accordance with a prescribed test plan for systems 1 and 2+)	Identification of incoming materials**	Depending on the nature of the materials	Every delivery
	Assembled system or relevant assembled components of the kit Reaction to fire	2.4.1	When starting the production process of the product or when starting a new production line
	Sheet: ** Appropriate characteristics according to annex B of EN 13707, EN 13967, EN 13969, EN 13956 and EN 14041		Appropriate characteristics according to annex B of EN 13707, EN 13967, EN 13969, EN 13956 and EN 14041
	Adhesive: ** According to the provisions for FPC in EN 12004 or other relevant standards		According to the provisions for FPC in EN 12004
Initial type testing of the product for systems 2+ and 4*	No tests necessary when the test leading to an ETA are done on products coming from the production process which is related with the ETA	-	-
	Identification of components** Appropriate characteristics according to annex B of EN 13707, EN 13956 and EN 14041 or EN 12004	See chapter 5	When starting the production process of the product or when starting a new production line

*) In case of system 4 there is no requirement for reaction to fire testing, see footnote *** of table 4 or class F

***) For components already CE marked according to relevant standards no further tasks by the kit manufacturer are necessary

3.2.1.1 Factory production control (FPC)

The manufacturer shall exercise permanent internal control of production. Elements controlling the production process include testing of materials before during and at the end of that process. All the elements, requirements and provisions adopted by the manufacturer shall be documented in a systematic manner in the form of written policies and procedures (See chapter 4 MTD). This production control system shall ensure that the product is in conformity with the European Technical Approval (ETA).

Manufacturers having an FPC system which complies with EN ISO 9001 **and** which addresses the requirements of an ETA are recognised as satisfying the FPC requirements of the Directive.

3.2.1.2 Testing of samples taken at the factory

These tests refer to finished product coming out of the production process. When the requirements of the FPC are fulfilled it is not necessary to have any more tests on samples taken at the factory.

3.2.1.3 Initial Type Testing (ITT)

Approval tests will have been conducted by the approval body or under its responsibility (which may include a proportion conducted by a laboratory or by the manufacturer, witnessed by the approval body) in accordance with section 2 of this ETAG. The approval body will have assessed the results of these tests in accordance with section 2 of this ETAG, as part of the ETA issuing procedure.

These tests should be used for the purposes of Initial Type Testing⁴ if they are done on samples coming from the current production process of the manufacturer which is referred to in the ETA. So further test are not necessary.

If the approval tests are done on samples e.g. of a prototype or if a new production line is started at the beginning of the new production process, an additional ITT is necessary.

3.2.1.4 *Declaration of Conformity*

When all the criteria of the Conformity Attestation on the basis of the tasks of the manufacturer and the tasks of the notified body (Certification) are satisfied the manufacturer shall make a Declaration of Conformity and has to assign the product with the CE-mark (see Chapter 3.3).

⁴ In this respect Approval Bodies shall be able to have open arrangements with relevant Notified Bodies to avoid duplication, respecting each others responsibilities.

3.2.2 Tasks of the notified body (control plan)

Table 6: Tasks of the notified body

Type of control		Test or control method	Minimum extent/frequency of control
AoC element (acc. to CPD Annex III.1)	Product, raw/constituent material, product component and characteristic concerned		
Initial type testing of the product (for systems 1 and 3)	No tests necessary when the test leading to an ETA (see approval testing in chapter 2) are done on products coming from the production process which is related with the ETA	-	-
	Reaction to fire of the kit	2.4.1	When starting the production process or when starting a new production line
Initial inspection of factory and of factory production control (for systems 1 and 2+)	Inspection of the factory and the factory production control of the manufacturer as described in the MTD and the control plan	Control of devices and equipment and the documentation of the FPC	When starting the production process or when starting a new production line
Continuous surveillance, assessment and approval of the factory production control (for systems 1 and 2+)	Surveillance, assessment and approval of the factory production control of the manufacturer as described in the MTD and the control plan	Control of the documentation of the FPC	Once (twice) a year

3.2.2.1 Initial Type Testing (ITT)

Approval tests will have been conducted by the approval body or under its responsibility (which may include a proportion conducted by a laboratory or by the manufacturer, witnessed by the approval body) in accordance with section 2 of this ETAG. The approval body will have assessed the results of these tests in accordance with section 2 of this ETAG, as part of the ETA issuing procedure.

These tests should be used for the purposes of Initial Type Testing⁵ if they are done on samples coming from the current production process of the manufacturer, which is referred to in the ETA. So further tests are not necessary.

If the approval test are done on samples e.g. of a prototype or if a new production line is started at the beginning of the of the new production process an additional ITT are necessary.

⁵ In this respect Approval Bodies shall be able to have open arrangements with relevant Notified Bodies to avoid duplication, respecting each others responsibilities.

3.2.2.2 Assessment of the factory production control system - initial inspection and continuous surveillance

The assessment of the factory production control system is the responsibility of the notified body.

The assessment shall be carried out of each production unit to demonstrate that the factory production control is in conformity with the ETA and any subsidiary information. This assessment shall be based on an initial inspection of the factory.

Subsequently continuous surveillance of factory production control is necessary to ensure continuing conformity with the ETA.

It is recommended that surveillance inspections be conducted once a year but if necessary i.e. if the results of the first inspection is unsatisfactory it may be required to be done more often e.g. twice per year.

3.2.2.3 Certification of product or Factory Production Control

When the criteria of the assessment of the factory production control are fulfilled the notified body shall issue the Certification of the product (system 1) or the Certification of the Factory Production Control (system 2+).

3.3 CE marking and accompanying information

According to Council Directive 93/68/EEC⁶ the CE marking consists of the letters "CE", followed by the identification number of the notified certification body, where applicable (*for AoC systems 1 and 2+*).

The ETA shall indicate the information to accompany the CE marking, i.e.

- The name or identifying mark of the producer and the manufacturing plant,
- The last two digits of the year in which the CE marking was affixed,
- For AoC systems 1: the number of the EC certificate of conformity for the product,⁷
- For AoC systems 2+ : the number of the EC certificate for the FPC,
- The number of the European technical approval,
- Number of ETAG (ETAG 022).

Example of CE-Marking and accompanying information:

 nnnn	"CE"-symbol Number of Notified Body (<i>for AoC systems 1 and 2+</i>)
Any Company Street 1 Country Plant 1 Yy nnnn-CPD-xxxx	Name and address of the ETA-holder or his representative established in the EEA and of the plant where the kit was manufactured Two last digits of year of affixing CE Marking Number of EC certificate of conformity (<i>for AoC systems 1</i>) or EC certificate for the FPC (<i>for AoC systems 2+</i>)
ETA-YY/WWWW ETAG 022 part 2	ETA Number ETAG Reference

⁶ .Official Journal of the European Communities no L 220, 30/8/1993 p. 1.

⁷ According to Guidance Paper D (*this is not envisaged in the CPD itself*)

4 ASSUMPTIONS UNDER WHICH THE FITNESS FOR THE INTENDED USE IS ASSESSED

4.1 Manufacturing of the kit

The actual manufacturing of the kit is performed on site. The Manufacturers Technical Dossier will describe the manufacturing of the components constituting the kit.

4.2 Packaging, transport, storage of the kit

The components of the watertight covering kit shall be protected from damage and excessive exposure to harmful actions.

The components shall be handled and stored with care and be protected from accidental damage.

The manufacturers installation guide shall contain information on proper storage, e.g. storage temperature, way of storage.

4.3 Installation of the kit in the works

The incorporation into the works is in fact the manufacturing of the wet room waterproofing as an assembled system.

The works in which the covering kit is installed are deemed to satisfy the Essential Requirements when that kit is assessed and declared fit for use and when the design and application rules specified by the applicant are fulfilled. In general the proper incorporation, assembly, application and installation therefore should be possible under practical circumstances.

The Manufacturers Technical Dossier shall include at least the following information:

- Definition of acceptable surfaces
- Preparation of the substrate (cleaning, moisture content, flatness, texture, maximum allowed cracks etc.
- Method of application, order of application
- Guidance on details, such as water tightness around pipe penetrations, floor gullies, inside and outside corners, connection between floor and wall, sealing over joints in the substrate etc.
- joints in the substrates
- Information on protection of watertight covering prior to installation of wearing surface and how work can be interrupted

The installation guide shall describe how to obtain a continuous layer of a possible primer on different substrates, where the primer is intended to enhance the water vapour resistance. In case this guidance is not provided, the test according to sec. 2.4.3.1 should be carried out on the sheet only.

4.4 Use, maintenance, repair

Guidance for use, maintenance and possibly repair shall be a part of the manufacturers installation guide and the assessment of the fitness for use is based on the assumption that normal maintenance of the watertight covering kit is performed.

For kits without a wearing surface the maintenance shall include cleaning, as necessary, with normal cleaning agents compatible with the watertight sheet followed by rinsing with water.

The assessments covered by this ETAG assume that the kit is subject only to basic cleaning agents (not acid) and that the kit is not used for intended uses with a requirement for an extreme resistance to biological and chemical agents.

5 IDENTIFICATION OF THE CONSTRUCTION PRODUCT

5.1 Means of identification

The kit and its components which are the subject of the technical approval shall be identified by:

- Testing of product characteristics of the system and/or components as laid down in the tables of this chapter.
- Fingerprinting.
- Formulation.
- Manufacturing process parameters.
- Calculations, details, drawings.

Even though all testing is performed on the kit, the identification of the kit is subject to the identification of the components of the kit.

There may be four main components of the flexible sheet kit; membrane, primer, adhesive and reinforcement, which are dealt with in the following.

5.2 Product characteristics used for identification checking

5.2.1 Flexible sheet

At least the following characteristics should be used for identification,:

- Visual defects
- Dimensions
- Mass pr. unit area
- Dimensional stability
- Tensile properties
- Water vapour
- Resistance to impact
- Resistance to tear (nail)
- Flexibility/foldability

Products CE marked according to relevant standards already include the above mentioned identification criteria.

5.2.2 Adhesives

The adhesives shall be designated according to EN 12004.

For identification purposes the following test is performed on the adhesives covered by the ETA:

5.2.2.1 Thermographic analysis

5.2.2.1.1 Method of verification

The analysis shall be carried out at air atmosphere, temperature increase rate 5 °C/min, maximum temperature 1000 °C.

On the basis of the thermographic analysis the ash content and dry extract are determined.

5.2.2.1.2 Method of assessing and judging

The result of the analysis shall be reported in the form of a TG graph together with relevant parameters and description of the preparation of the samples.

Ash content and dry extract shall be given as declared value.

5.2.3 Primers

Number	Characteristic	Verification method: Clause ...	Criteria for product identity:
(1)	(2)	(3)	(4)
5.2.3.1	Infrared spectrometry	5.2.3.1.1	5.2.3.1.2
5.2.3.2	Viscosity	5.2.3.2.1	5.2.3.2.2
5.2.3.3	Density	5.2.3.3.1	5.2.3.3.2
5.2.3.4	pH-value	5.2.3.4.1	5.2.3.4.2

Table 7 Product characteristics, methods of verification and criteria used for checking the product identity

5.2.3.1 Infrared spectrometry of the primer

5.2.3.1.1 Method of verification

The infrared spectrometry is carried out at a resolution of 4 cm^{-1} with a measuring range of 4 000 - 400. 32 scannings are made.

5.2.3.1.2 Method of assessing and judging

The result of the analysis shall be reported in the form of an IR graph together with relevant parameters and description of the preparation of the samples.

5.2.3.2 Viscosity

5.2.3.2.1 Method of verification

The viscosity shall be determined according to a method appropriate for the primer composition.

5.2.3.2.2 Method of assessing and judging

Declared value

5.2.3.3 Density

5.2.3.3.1 Method of verification

The density shall be determined according to a method appropriate for the primer composition.

5.2.3.3.2 Method of assessing and judging

Declared value

5.2.3.4 pH-Value

5.2.3.4.1 Method of verification

The pH-value shall be determined according to a method appropriate for the primer composition.

5.2.3.4.2 Method of assessing and judging

Declared value

6 FORMAT OF ETAs ISSUED ON THE BASIS OF THE ETAG

European technical approvals issued on the basis of this ETAG/CUAP shall be in accordance with the ETA format given in the Guidance to the ETAG/CUAP writers.

Specifically, the ETA shall include the test results of the harmonised characteristics or npd according to table 2. Particularly the ETA shall specify the intended use in relation to substrates and joints as described in paragraph 1.2.2 of the guideline.

7 REFERENCE DOCUMENTS

Commission Guidance Paper C	The treatment of kits and systems under the construction products directive
EN 13501-1:2007	Fire classification of construction products – Part 1: Classification using test data from reaction to fire tests
EN/ISO 12572: June 2001	Hygrothermal performance of building materials and products - Determination of water vapour transmission properties
ETAG 005: March 2001, revision March 2004	ETA Guideline for Liquid applied roof waterproofing kits
prEN 14891: February 2004	Liquid applied waterproofing membranes for use beneath ceramic tiling – Definitions, specifications and test methods
prEN 1062-7: July 2003	Paints and varnishes – coating materials and coating systems for exterior masonry and concrete – Part 7: Determination of crack bridging properties, test methods
EOTA Technical Report 0013: May 2004	Determination of crack bridging capability
EN 13813: October 2002	Screed material and floor screeds – Screed material – Properties and requirements
EN 660-1: 1999	Resilient floor coverings – Determination of wear resistance. Part 1: Stuttgart test
EN 660-2: 1999	Resilient floor coverings – Determination of wear resistance. Part 2: Frick-Taber test
EEC Decision 2003/655/EC	Mandate for Watertight covering kits for wet room floors and walls
EN 12004: March 2001	Adhesives for tiles – Definitions and specifications
EN 14041	Resilient, textile and laminate floor coverings - Essential characteristics
EN 13707	Flexible sheets for waterproofing - Reinforced bitumen sheets for roof waterproofing - Definitions and characteristics
EN 13956	Flexible sheets for waterproofing - Plastic and rubber sheets for roof waterproofing - Definitions and characteristics
EN 13967	Flexible sheets for waterproofing - Plastic and rubber damp proof sheets including plastic and rubber basement tanking sheet - Definitions and characteristics

EN 13969	Flexible sheets for waterproofing - Bitumen damp proof sheets including bitumen basement tanking sheets - Definitions and characteristics
EN 14411	Ceramic tiles - Definitions, classification, characteristics and marking
EN ISO 11925-2	Reaction to fire tests - Ignitability of building products subjected to direct impingement of flame - Part 2: Single-flame source test
EN 13553	Resilient floor coverings - Polyvinyl chloride floor coverings for use in special wet areas - Specification
EN 1931	Flexible sheets for waterproofing - Bitumen, plastic and rubber sheets for roof waterproofing - Determination of water vapour transmission properties
EN 1928	Flexible sheets for waterproofing - Bitumen, plastic and rubber sheets for roof waterproofing - Determination of watertightness
EN 684	Resilient floor coverings - Determination of seam strength
EN 12317-1	Flexible sheets for waterproofing - Part 1: Bitumen sheets for roof waterproofing - Determination of shear resistance of joints
EN 12317-2	Flexible sheets for waterproofing - Determination of shear resistance of joints - Part 2: Plastic and rubber sheets for roof waterproofing
EN 435	Resilient floor coverings - Determination of flexibility
EN 1107-1	Flexible sheets for waterproofing - Part 1: Bitumen sheets for roof waterproofing - Determination of dimensional stability
EN 1107-2	Flexible sheets for waterproofing - Determination of dimensional stability - Part 2: Plastic and rubber sheets for roof waterproofing
EN 1296	Flexible sheets for waterproofing - Bitumen, plastic and rubber sheets for roofing - Method of artificial ageing by long term exposure to elevated temperature
EN 12311-1	Flexible sheets for waterproofing - Part 1: Bitumen sheets for roof waterproofing - Determination of tensile properties
EN 12311-2	Flexible sheets for waterproofing - Determination of tensile properties - Part 2: Plastic and rubber sheets for roof waterproofing
EN 1847	Flexible sheets for waterproofing - Plastics and rubber sheets for roof waterproofing - Methods for exposure to liquid chemicals, including water
EN 13859-1	Flexible sheets for waterproofing - Definitions and characteristics of underlays - Part 1: Underlays for discontinuous roofing
EN 428	Resilient floor coverings - Determination of overall thickness

EN 429	Resilient floor coverings - Determination of the thickness of layers
EN 1849-1	Flexible sheets for waterproofing - Determination of thickness and mass per unit area - Part 1: Bitumen sheets for roof waterproofing
EN 1849-2	Flexible sheets for waterproofing - Determination of thickness and mass per unit area - Part 2: Plastic and rubber sheets
EN ISO 9001	Quality management systems - Requirements